

Synthesis of Zeolitic Imidazolate Framework-8 Using Glycerol Carbonate

Masaki Itatani, Norbert Németh, Nadia Valletti, Gábor Schuszter, Prisco Prete, Pierandrea Lo Nostro, Raffaele Cucciniello,* Federico Rossi,* and István Lagzi*



Cite This: *ACS Sustainable Chem. Eng.* 2023, 11, 13043–13049



Read Online

ACCESS |



Metrics & More




Article Recommendations



Supporting Information

ABSTRACT: In this study, we show that glycerol carbonate (GlyC), a bio-based derivative of glycerol, can be used as a suitable green solvent for the synthesis of metal–organic frameworks (MOFs). In particular, a zinc-based zeolitic imidazolate framework-8 (ZIF-8) was synthesized by exploring several different experimental conditions (in terms of temperature, reaction time, and reactants' concentrations) to find that the yield of the reaction and the quality of the products, measured in terms of crystallinity, surface area, and porosity, were in line with those obtained in the most commonly (non-green) used solvents. GlyC was also found to be reusable for several cycles, maintaining the same original quality as a solvent for the synthesis. Finally, some indicators for the assessment of the greenness of a process (E-factor and PMI) revealed a milder environmental impact of GlyC with respect to other solvents.

KEYWORDS: metal–organic framework (MOF), zeolitic imidazolate framework (ZIF), recycle, solvents, porous materials

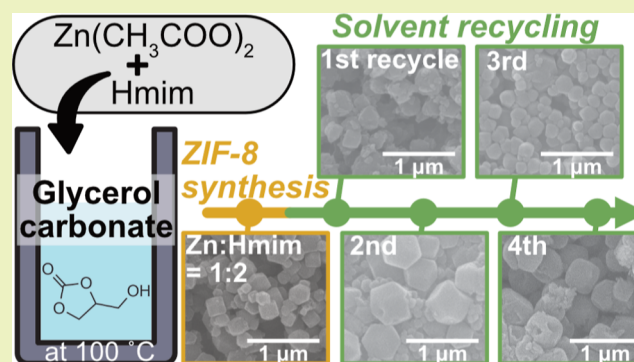

INTRODUCTION

Zeolitic imidazolate framework-8 (ZIF-8) is one of the representative materials of metal–organic frameworks (MOFs),¹ a class of materials composed of metal cations coordinating organic ligands. Due to their special structure, MOFs have a high specific surface area and large pore size, which render them a good candidate for gas storage, separation, chromatography, electronic applications, and drug delivery.^{2–5} In this respect, many efforts were made to control the ZIF-8 crystal morphology and crystal size distribution. To pursue this goal, the control of crystal size distribution was achieved using different strategies such as the adjustment of the reactant ratios, the incorporation of additives (e.g., trialkyl amine, cetyltrimethylammonium bromide, formate, etc.), the sources of Zn(II) ions, and the proper selection of the synthetic method (sono-crystallization, micromixer, ionothermal microwave-assisted synthesis, microwave irradiation).⁶ In contrast, the research on new green and bio-based solvents for MOF synthesis is still limited. Indeed, methods using amide-type solvents (e.g., dimethylformamide, DMF) are the most used for the synthesis of ZIF-8⁷ with scant examples based on more environment-friendly alternatives, such as methanol⁸ or water.⁹ When water is used as a solvent, the synthesis should be carried out in an alkaline environment usually by applying an excess of organic linkers.^{10–13} Rapid synthesis methods (<1 h) at room temperature are also presented in the literature, however, in this case, the size of the formed crystals is less than

100 nm.¹⁴ In fact, DMF is a toxic, fossil-based, polar, and aprotic solvent characterized by a high dielectric constant and a high boiling point, features that favor the progress of the synthetic process¹⁵ but may pose concerns on the environmental impacts.

To overcome this limitation and with the ambitious idea to substitute DMF with greener alternatives, in this work we report for the first time the preparation of crystalline ZIF-8 in glycerol carbonate (GlyC). GlyC (4-hydroxymethyl-2-oxo-1,3-dioxolane) has attracted increasing interest as one of the most investigated bio-based compounds with many interesting applications in different fields, such as in the synthesis of new chemicals,^{16,17} the manufacturing of polymers, building blocks for drug preparation, surfactants, cosmetics, and detergent industries. Moreover, the use of GlyC fully respects the 7th principle of Green Chemistry^{17–22} due to its preparation from glycerol through transcabonation with dimethyl carbonate. Because of its physicochemical properties (Table S1 in [Supporting Information](#)), GlyC is also used as a biodegradable, low-volatile organic solvent with low toxicity

Received: May 15, 2023

Revised: July 27, 2023

Published: August 21, 2023



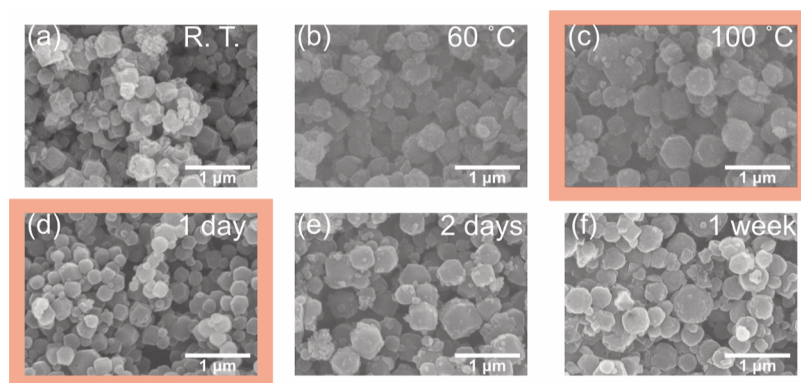


Figure 1. SEM micrographs of synthesized ZIF-8 after 2 days of reaction using 10 mM of NaOH at various temperatures: (a) room temperature (~ 20 °C), (b) 60, and (c) 100 °C. Generated ZIF-8 at 100 °C using 10 mM of NaOH for various synthesis times: (d) 1 day, (e) 2 days, and (f) 1 week. All reactions were carried out using $[\text{Zn}(\text{OAc})_2] = 10$ mM and $[\text{Hmim}] = 40$ mM. Panels (c,d) are framed in orange to highlight the optimal conditions in terms of temperature and reaction time.

having a high dielectric constant and dipole moment.²³ Indeed, GlyC shows relevant and promising properties to overcome the limitations related to DMF for ZIF-8 preparation. In this work, to further assess the advantages concerning the use of GlyC for this purpose, solvent recyclability experiments were carried out, and both simple E-Factor (sEF) and process mass intensity (PMI) were calculated and discussed.

EXPERIMENTS

Reagents and Materials. Dimethyl carbonate (DMC), glycerol (>99%), sodium carbonate (Na_2CO_3), zinc acetate dihydrate (>99%, $\text{Zn}(\text{OAc})_2 \cdot 2\text{H}_2\text{O}$), 2-methylimidazole (99%, Hmim), sodium hydroxide (>98%, NaOH), dimethyl sulfoxide (DMSO), and DMF were purchased from Merck (Darmstadt, Germany).

Synthesis and Characterization of GlyC. GlyC was prepared by glycerol transcarbonation with DMC in the presence of Na_2CO_3 as a catalyst.^{24,25} 900 g (10.0 mol) of DMC, 300.6 g of glycerol (3.34 mol), and 1.06 g of Na_2CO_3 (1.0 mol) were introduced into a 2 L three-necked flask equipped with a mechanical stirring, a steam condenser, and a temperature sensor. The mixture was stirred and refluxed (75 °C) for 2 h. Afterward, the catalyst was filtered off and the excess of dimethyl carbonate and the produced methanol were distilled under reduced pressure. GlyC was obtained as a colorless viscous liquid (394 g) with a purity of 96% [nuclear magnetic resonance (NMR) analysis]. The NMR spectra were collected with a Bruker AVANCE-400 (100 ^{13}C) spectrometer using deuterated DMSO as the solvent (for details see the Supporting Information).

Synthesis and Characterization of ZIF-8. A given amount of $\text{Zn}(\text{OAc})_2 \cdot 2\text{H}_2\text{O}$ and Hmim were dissolved separately in the synthesized pure GlyC or GlyC containing sodium hydroxide (0.01 M) by sonicating and heating at 60–70 °C, respectively. The reason for the addition of sodium hydroxide is that it favors the formation of ZIF-8 crystals not only in water but also in less polar solvents.^{26,27} Then, these mixtures were allowed to stand at room temperature to cool down, and each solution was degassed using N_2 stream. The two solutions were then mixed. The reaction was carried out in glass vials at three different temperatures, namely room temperature (~ 20 °C), 60, and 100 °C, using a heating block. Vials were covered with septum caps. The precipitate was allowed to settle for different periods of time (1, 2, and 7 days) and the generated particles were collected by centrifugation at 7000 rpm, rinsed one time with water and three times with DMF to remove unreacted chemical species. In the recycle experiments, the solvent was collected after the first centrifugation, filtered through an agarose membrane (0.45 μm pore size) to remove large particles and aggregates and finally used for a new synthesis in an iterative procedure.

To characterize the solid precipitate samples, the microstructure was investigated by scanning electron microscopy (SEM) and the

crystalline phase assignment relied on powder X-ray diffraction (PXRD) measurements. The nitrogen adsorption data evaluated via Brunauer–Emmett–Teller (BET) and Barrett–Joyner–Halenda (BJH) methods provided us with the specific surface area and pore size distribution, respectively. A Hitachi S-4700 instrument was used at a 20 kV acceleration voltage and 10 μA current to take SEM micrographs. Prior to that, the samples were spread on a carbon tape, and gold sputtering (180 s, 18 mA) was applied to increase their conductance. PXRD diffractograms were registered by a Rigaku MiniFlex II desktop X-ray diffractometer at room temperature. The solid samples were spread on a silicon crystal cut holder to minimize the background noise. The measurements were conducted with a 30 kV accelerating voltage and 15 mA current. Scanning speed was set to 4°/min within $2\theta = 5$ –50° range applying 0.02° step size. As a radiation source, we used a standard Cu $K\alpha$ ($\lambda = 0.1542$ nm) beam. Before the nitrogen adsorption measurements, samples were degassed for 2 h at 180 °C (previous studies showed that higher temperature degraded the samples' microstructure). Nitrogen adsorption data were collected with a Nova 3000 (Quantachrome, USA) instrument. The range of 0.05–0.35 relative pressure was used to determine the specific surface area, and the desorption band of the isotherm was applied for the BJH method.

Calculation of sEF, PMI, and Yield. Concerning the preparation of crystalline ZIF-8 and to enlarge the discussion about the reaction greenness, sEF and PMI calculations were carried out. Data obtained in the presence of GlyC as a solvent were counterposed to those reported in the literature for DMF²⁸ and water.¹⁰ PMI values were also recalculated after the recovery of all the chemicals (PMIr).²⁹

$$\text{sEF} = \frac{\text{mass waste(g)}}{\text{mass ZIF-8(g)}} \quad (1)$$

$$\text{PMI} = \frac{\sum (\text{mass reagents(g)} + \text{mass solvent(g)} + \text{mass water(g)})}{\text{mass ZIF-8(g)}} \quad (2)$$

$$\text{PMIr} = \left[\sum (\text{mass reagents(g)} + \text{mass solvent(g)} + \text{mass water(g)}) - \sum (\text{mass recovered solvents(g)} + \text{mass ZIF-8(g)}) \right] / [\text{mass ZIF-8(g)}] \quad (3)$$

Also, a mass yield of synthesized ZIF-8 particles in GlyC was calculated by the following equation

$$\text{yield(\%)} = \frac{\text{experimental obtained mass ZIF-8(g)}}{\text{theoretic mass ZIF-8(g)}} \times 100 \quad (4)$$

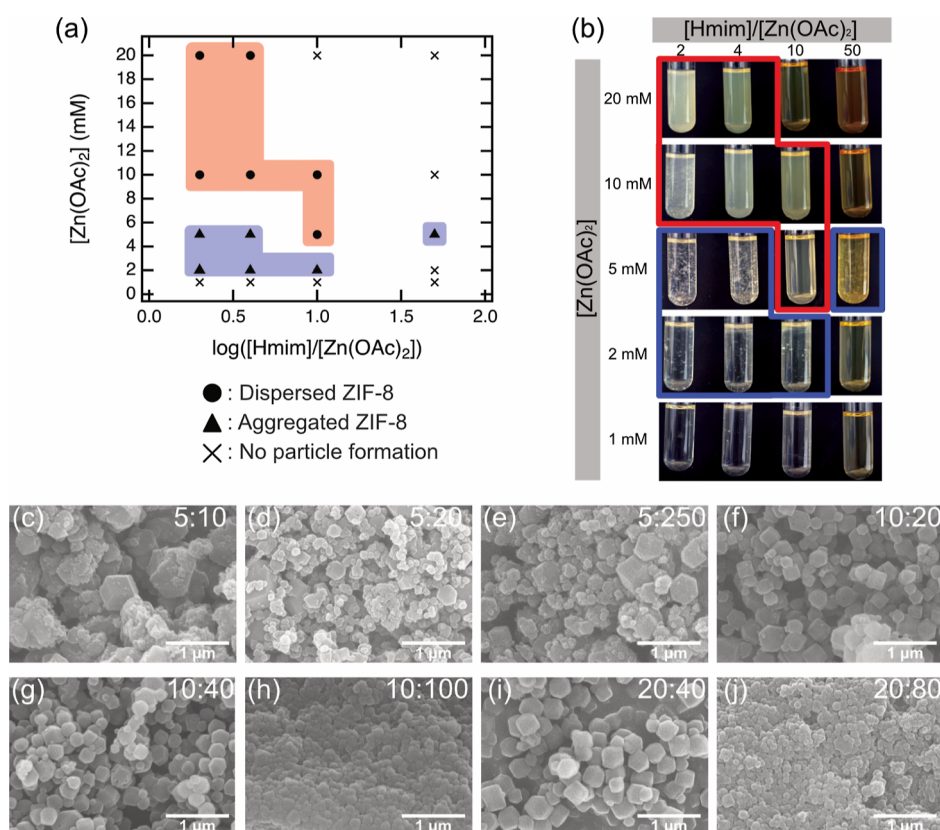


Figure 2. (a) Effect of the initial concentration of the reactants on the reaction and (b) photographs of the reaction mixture after 1 day at 100 °C. (c) SEM micrographs of ZIF-8 particles at $\Theta = 100$ °C, $t = 1$ day, and $[\text{NaOH}] = 0.01$ M using $[\text{Zn}(\text{OAc})_2]/[\text{Hmim}] =$ (c) 5:10 mM, (d) 5:20 mM, (e) 5:250 mM, (f) 10:20 mM, (g) 10:40 mM, (h) 10:100 mM, (i) 20:40 mM, and (j) 20:80 mM, respectively.

where the “theoretic mass of ZIF-8” is the theoretic yield calculated by a given amount of limited reagent (namely, zinc ions in this study) and the empirical formula of ZIF-8, namely $\text{Zn}(\text{Hmim})_2$.

RESULTS AND DISCUSSION

First, some preliminary experiments were carried out to obtain the optimal experimental conditions for the synthesis. We investigated the effect of temperature and of the total reaction time using fixed initial concentrations for the reactants: 10 mM zinc salt and four-fold excess of Hmim ($[\text{Zn}(\text{OAc})_2] = 10$ mM and $[\text{Hmim}] = 40$ mM).^{30–33} SEM micrographs in Figure 1 show that crystals having the typical geometry of ZIF-8 form in all experimental conditions when GlyC is used as the reaction medium. In particular, Figure 1a–c shows that the high temperature favors the formation of bigger and more crystalline particles. Concerning the reaction time, we found that 1 day was the optimal lapse, as illustrated in Figure 1d–f. This finding is in good accordance with the most widely applied synthesis time of ZIFs in hydro- and solvothermal methods.³⁴ An increased reaction time would lead to the formation of bigger particles on average; however, after 2 days, the bigger crystals were covered by smaller particles (Figure 1e). After 1 week of reaction, the edges of the crystals became less sharp due to the degradation of the sample.³⁵ Based on these experiments, the optimal experimental conditions for the generation of ZIF-8 in GlyC were found to be the same as those obtained in other solvents, namely high temperature and synthesis time of 1 day.^{1,36}

The next step was to explore whether the concentration of the reactants affects the size and the morphology of the ZIF-8

crystals, keeping the same experimental conditions ($\Theta = 100$ °C, $t = 1$ day). Figure 2a summarizes the visual appearance of the colloidal suspension and the morphology of the crystals characterized by SEM measurements. At a low concentration of zinc ions (1 mM), no crystallization was observed. Based on the SEM measurements, the optimal crystallinity was obtained with the ratios $[\text{Zn}(\text{OAc})_2]/[\text{Hmim}] = 10:20$ mM, 10:40 mM, and 20:40 mM (Figure 2f,g,i). This is an interesting finding because, in most of the studies, the ratio of Hmim to Zn to generate ZIF-8 is greater than the stoichiometric ratio, which is 2:1. So far, the synthesis of ZIF-8 with a stoichiometric ratio of reactants was achieved using either a great amount of base³⁷ or a jet-mixer reactor.³⁸ In contrast, GlyC allowed the synthesis of ZIF-8 at the stoichiometric ratio, in mild reaction conditions, and using the simple solvothermal setup. Also, at the ratio of $[\text{Zn}(\text{OAc})_2]/[\text{Hmim}] = 10:20$ mM, the mass yield of the product was 57.1%, which is comparable to or even higher than that obtained using the common solvothermal setup with DMF and methanol as solvents.^{28,36} Further investigations on the crystalline phase assignment, specific surface area, pore volume, and recyclability measurements were conducted with a ratio of $[\text{Zn}(\text{OAc})_2]/[\text{Hmim}] = 10:20$ mM, i.e., at the lowest concentration of Hmim.

After the synthesis at a high concentration of Hmim (>100 mM), the solution turned to a yellowish color, as reported in Figure 2b. This was likely due to reactions of Hmim with the base and of GlyC with Hmim. In detail, the reaction of Hmim with NaOH leads to the formation of sodium 2-methylimidazole which is the active organic ligand for ZIF-8 synthesis. This molecule shows significant absorption in the UV–vis

range, depending on the solvent. Moreover, preliminary experiments carried out using sole Hmim and GlyC reveal the formation of side products which will be characterized in future work (more details in the Supporting Information). In passing, we recall that GlyC undergoes a yellowing degradation in the presence of bases.³⁹ However, in the optimal concentration range for the formation of ZIF-8 crystals, the effect of the side reactions was negligible due to the relatively low concentrations of both cations and linkers.

To characterize the solid products, we performed PXRD and nitrogen adsorption measurements (Figure 3). The recorded PXRD pattern showed excellent crystallinity and a good match with the data reported in the literature (Figure 3a).³⁷ The average specific surface area of the ZIF-8 crystals was found to be $660 \text{ m}^2 \text{ g}^{-1}$ which is roughly 50% less than the usual value of the samples synthesized in other organic solvents, e.g., DMF.^{1,36,40} The isotherm resembles type IV isotherms without

the plateau near unity relative pressure. Type IV isotherms are characteristic of mesoporous materials, where the typical pore diameter, d , is between 20 and 500 Å. The absence of the plateau and thus the unlimited growth of the absorbed volume at higher relative pressures is an indicator of the presence of macropores ($d > 500 \text{ Å}$). The same conclusion can be drawn from Figure 3c, i.e., the most characteristic pore size is ca. 50 Å, which is representative of mesoporous ZIFs.¹² The distribution is relatively wide, and the population of pores of 40–100 Å diameter is equally important. Macropores ranging from 500 to 1000 Å can be found, but their abundance is low. Due to the features of the measurement, we do not consider the pores below 20 Å. The type H3 hysteresis is characteristic of pores surrounded by plates. Since the *dia* (diamond-like) polymorph of ZIF-8 is plate-like and less porous than the sodalite-like (SOD) polymorph, the hysteresis loop together with the relatively low specific surface area suggests that the *dia* polymorph is also present in the sample. The total pore volume is $0.58 \text{ cm}^3 \text{ g}^{-1}$ (Figure 3b).

According to the circular economy approach, the recyclability of the solvent is one of the crucial issues that must be considered.^{13,27,41,42} We performed the sequential synthesis of ZIF-8 by reusing the same sample of GlyC as a solvent for several cycles. SEM measurements (Figure 4) and yield calculations based on eq 4 revealed that the formation of crystals with different yields varied from the first to fourth cycle: 52.8% (first), 58.8% (second), 62.8% (third), and 74.1% (fourth cycle), respectively. Increasing yield could be due to remaining and accumulating unreacted species (Zn^{2+} and Hmim) in the system after each cycle.

PMI has been proposed as a key mass-based metric.⁴³ In the last years, several studies concerning the adoption of PMI have been published to analyze the process's efficiency in terms of mass.⁴⁴ We used both sEF and PMI not only to critically address the impacts of GlyC utilization and recycling but also to compare the ZIF-8 preparation in the presence of different solvents (GlyC, water, and DMF). However, it was recognized that these metrics did not address concerns regarding the toxicity and safety of the feedstock materials or wastes.⁴⁵ The preparation of ZIF-8 in GlyC is performed with a sEF value of 1.2 after five consecutive reaction cycles. Indeed, the possibility to fully recycle the reaction mixture during five consecutive cycles gives an sEF, for each of these cycles, equal to 0 in agreement with the requirements of the circular approach.⁴¹ Results obtained in DMF and water gave an sEF of 9.4 and 11.2, respectively. These outcomes can be related to the lower ZIF-8 yields in DMF (30.5% w/w) using an Hmim/ Zn^{2+} mole ratio of 8²⁸ and to a high excess of Hmim (Hmim/ Zn^{2+} mole ratio of 40) in water (ZIF-8 yield = 97.5% w/w).¹⁰ The sEF did not address the impact of water and solvent as, instead, PMI does. Therefore, PMI values are higher than sEFs. PMI values, calculated on the first reaction cycle to compare the three different scenarios, are 1122 for GlyC, 67 for DMF, and 281 for water. Considering the GlyC recyclability the PMI calculated after five reaction cycles is 206. Furthermore, considering the GlyC recyclability, the PMI reaches the value of 2.8.²⁹ The obtained results clearly indicated the excellent impact of GlyC on the ZIF-8 synthesis by reducing the production of waste and through its recycling along four consecutive syntheses.

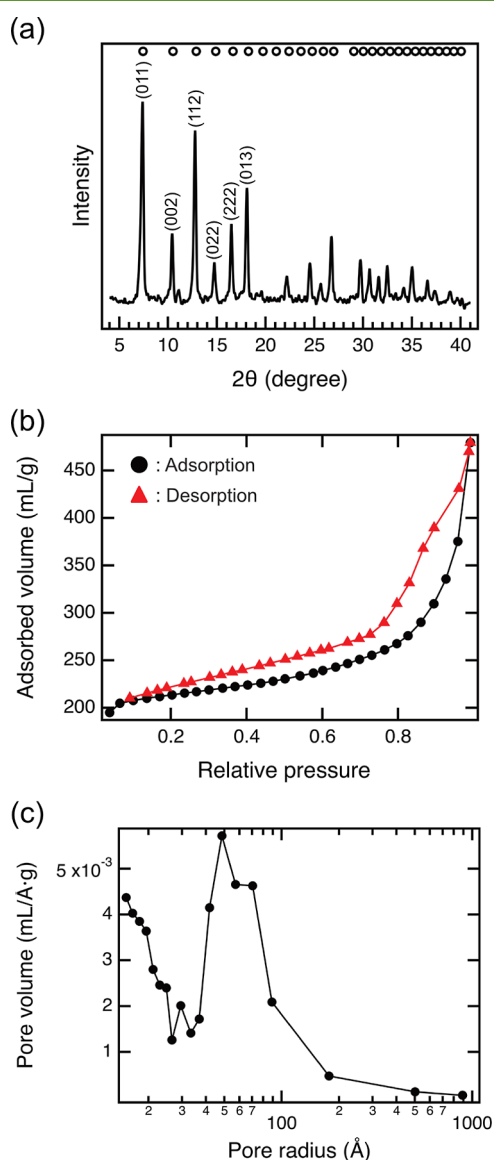


Figure 3. (a) PXRD pattern, (b) BET isotherm, and (c) BJH pore size distribution of ZIF-8 synthesized at 100 °C for 1 day with $[\text{Zn}(\text{OAc})_2] = 10 \text{ mM}$, $[\text{Hmim}] = 20 \text{ mM}$, and $[\text{NaOH}] = 10 \text{ mM}$. The open circles above the peaks in panel (a) indicate the reported diffractions of ZIF-8.³⁷

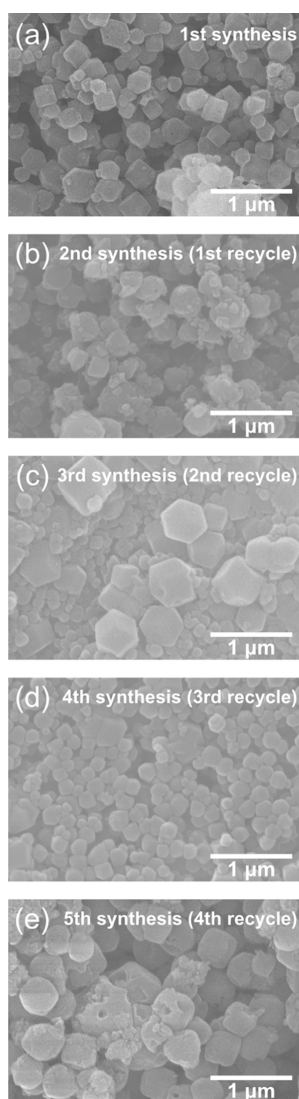


Figure 4. SEM micrographs of ZIF-8 synthesized in the first synthesis (a) and each recycle step: (b) first, (c) second, (d) third, and (e) fourth recycles. ZIF-8 was synthesized for every recycling experiment at 100 °C for 1 day with $[\text{Zn}(\text{OAc})_2] = 10 \text{ mM}$, $[\text{Hmim}] = 20 \text{ mM}$, and $[\text{NaOH}] = 10 \text{ mM}$.

CONCLUSIONS

In conclusion, we showed how an effective synthesis of technologically relevant materials, such as MOFs, can be successfully obtained in the bio-based solvent GlyC. Table 1 summarizes the characteristics of the ZIF-8 samples by using various methods of synthesis.^{1,36,46–49} The largest crystals (up to 200 μm) can be obtained in a solvothermal method using DMF. However, the microfluidic method generates particles with the largest specific surface area. The pore volume in all techniques spans between 0.4 and 0.7 $\text{cm}^3 \text{g}^{-1}$. In terms of yield and quality of the products, GlyC proved to be in line with the performances of other solvents, such as DMF and water, but having a milder environmental impact, as calculated by the sEF and the PMI. From a circularity point of view, the use of a derivative of glycerol for industrial applications can boost the use of bio-based chemicals and help the transition toward a more sustainable society.

Table 1. Comparison of the Sample Characteristics Obtained in Various Methods and Solvents for the Synthesis of ZIF-8^a

| synthesis method | particle size (μm) | S_{BET} ($\text{m}^2 \text{g}^{-1}$) | V_{pore} ($\text{cm}^3 \text{g}^{-1}$) | refs |
|--|---------------------------------|---|---|------|
| solvothermal (DMF) | 150–200 | 1370 | 0.51 | 1,36 |
| solvothermal (MeOH) | 3–5 | 1549 | 0.59 | 36 |
| hydrothermal (H ₂ O added TEA) | 0.1–1 | 1340 | | 46 |
| microwave-assisted (DMF) | 5–10 | 1250 | 0.53 | 36 |
| microwave-assisted (MeOH) | 0.33 | 61 | | 1,47 |
| sonochemical (DMF added TEA) | 0.3–0.5 | 1249 | 0.71 | 36 |
| mechanochemical | 3–15 | 1256 | 0.64 | 36 |
| microfluidic synthesis (DMF) | 5–15 | 1435 | 0.42 | 36 |
| microfluidic synthesis (H ₂ O) | 0.3–0.9 | 1730 | | 1,47 |
| dry-gel conversion (H ₂ O) | 0.3–0.4 | 1306 | 0.52 | 36 |
| electrochemical | <1.0 | 1500 | 0.60 | 1,47 |
| steam-assisted conversion (H ₂ O) | | 1470 | | 1,49 |
| solvothermal (GlyC) | 0.2–0.8 | 660 | 0.58 | |

^a S_{BET} and V_{pore} are specific surface area and pore volume, respectively. MeOH and TEA stand for methanol and triethanolamine, respectively.

ASSOCIATED CONTENT

Supporting Information

The Supporting Information is available free of charge at <https://pubs.acs.org/doi/10.1021/acssuschemeng.3c02876>.

Characterization of GlyC, sodium 2-methylimidazolate, and reaction byproducts (PDF)

AUTHOR INFORMATION

Corresponding Authors

Raffaele Cucciniello – Department of Chemistry and Biology, University of Salerno, Fisciano, Salerno 84084, Italy; Centro Interdisciplinare Linceo Giovani, Accademia Nazionale dei Lincei, 00165 Roma, Italy; orcid.org/0000-0002-3291-7273; Email: rcucciniello@unisa.it

Federico Rossi – Department of Physical Sciences, Earth and Environment, University of Siena, 53100 Siena, Italy; orcid.org/0000-0002-1854-532X; Email: federico.rossi2@unisi.it

István Lagzi – Department of Physics, Institute of Physics and ELKH-BME Condensed Matter Research Group, Budapest University of Technology and Economics, H-1111 Budapest, Hungary; orcid.org/0000-0002-2303-5965; Email: lagzi.istvan.laszlo@ttk.bme.hu

Authors

Masaki Itatani – Department of Physics, Institute of Physics, Budapest University of Technology and Economics, H-1111 Budapest, Hungary; orcid.org/0000-0003-1025-0452

Norbert Németh – Department of Physics, Institute of Physics and Department of Organic Chemistry and Technology, Budapest University of Technology and Economics, H-1111 Budapest, Hungary

Nadia Valletti – Department of Physical Sciences, Earth and Environment, University of Siena, 53100 Siena, Italy

Gábor Schuszter – Department of Physical Chemistry and Materials Science, University of Szeged, H-6720 Szeged, Hungary; orcid.org/0000-0002-9170-9933

Prisco Prete – Department of Chemistry and Biology, University of Salerno, Fisciano, Salerno 84084, Italy

Pierandrea Lo Nostro – Department of Chemistry “Ugo Schiff”, University of Firenze, Sesto Fiorentino, Florence 50019, Italy

Complete contact information is available at:

<https://pubs.acs.org/10.1021/acssuschemeng.3c02876>

Author Contributions

The manuscript was written through the contributions of all authors. All authors have given approval to the final version of the manuscript.

Notes

The authors declare no competing financial interest.

ACKNOWLEDGMENTS

This work was supported by the National Research, Development and Innovation Office of Hungary (K131425 and K138844), the Ministry of Culture and Innovation and the National Research, Development, and Innovation Office under Grant Nr. TKP2021-EGA-02, and the JSPS Postdoctoral Fellowship Program for Overseas Researchers (identification number 202260298). The technical assistance of Alessandra Sessa from the Università degli Studi di Salerno is deeply acknowledged. F.R. and I.L. gratefully acknowledge the COST action, EU CA17120 Chemobionics for funding a Short-Term Scientific Mission.

REFERENCES

- (1) Bergaoui, M.; Khalfaoui, M.; Awadallah-F, A.; Al-Muhtaseb, S. A Review of the Features and Applications of ZIF-8 and Its Derivatives for Separating CO₂ and Isomers of C₃- and C₄- Hydrocarbons. *J. Nat. Gas Sci. Eng.* **2021**, *96*, 104289.
- (2) Wang, Q.; Sun, Y.; Li, S.; Zhang, P.; Yao, Q. Synthesis and Modification of ZIF-8 and Its Application in Drug Delivery and Tumor Therapy. *RSC Adv.* **2020**, *10*, 37600–37620.
- (3) Lai, Z. Development of ZIF-8 Membranes: Opportunities and Challenges for Commercial Applications. *Curr. Opin. Chem. Eng.* **2018**, *20*, 78–85.
- (4) Paul, A.; Banga, I. K.; Muthukumar, S.; Prasad, S. Engineering the ZIF-8 Pore for Electrochemical Sensor Applications—A Mini Review. *ACS Omega* **2022**, *7*, 26993–27003.
- (5) Lo, Y.; Lam, C. H.; Chang, C.-W.; Yang, A.-C.; Kang, D.-Y. Polymorphism/Pseudopolymorphism of Metal–Organic Frameworks Composed of Zinc(II) and 2-Methylimidazole: Synthesis, Stability, and Application in Gas Storage. *RSC Adv.* **2016**, *6*, 89148–89156.
- (6) Bustamante, E. L.; Fernández, J. L.; Zamaro, J. M. Influence of the Solvent in the Synthesis of Zeolitic Imidazolate Framework-8 (ZIF-8) Nanocrystals at Room Temperature. *J. Colloid Interface Sci.* **2014**, *424*, 37–43.
- (7) Park, K. S.; Ni, Z.; Côté, A. P.; Choi, J. Y.; Huang, R.; Uribe-Romo, F. J.; Chae, H. K.; O’Keeffe, M.; Yaghi, O. M. Exceptional Chemical and Thermal Stability of Zeolitic Imidazolate Frameworks. *Proc. Natl. Acad. Sci. U.S.A.* **2006**, *103*, 10186–10191.
- (8) Venna, S. R.; Jasinski, J. B.; Carreon, M. A. Structural Evolution of Zeolitic Imidazolate Framework-8. *J. Am. Chem. Soc.* **2010**, *132*, 18030–18033.
- (9) Jian, M.; Liu, B.; Liu, R.; Qu, J.; Wang, H.; Zhang, X. Water-Based Synthesis of Zeolitic Imidazolate Framework-8 with High Morphology Level at Room Temperature. *RSC Adv.* **2015**, *5*, 48433–48441.
- (10) Kida, K.; Okita, M.; Fujita, K.; Tanaka, S.; Miyake, Y. Formation of High Crystalline ZIF-8 in an Aqueous Solution. *CrystEngComm* **2013**, *15*, 1794–1801.
- (11) Abdelhamid, H. N.; Zou, X. Template-Free and Room Temperature Synthesis of Hierarchical Porous Zeolitic Imidazolate Framework Nanoparticles and Their Dye and CO₂ Sorption. *Green Chem.* **2018**, *20*, 1074–1084.
- (12) Abdel-Magied, A. F.; Abdelhamid, H. N.; Ashour, R. M.; Zou, X.; Forsberg, K. Hierarchical Porous Zeolitic Imidazolate Frameworks Nanoparticles for Efficient Adsorption of Rare-Earth Elements. *Microporous Mesoporous Mater.* **2019**, *278*, 175–184.
- (13) Şahin, F.; Topuz, B.; Kalıpçılar, H. Synthesis of ZIF-7, ZIF-8, ZIF-67 and ZIF-L from Recycled Mother Liquors. *Microporous Mesoporous Mater.* **2018**, *261*, 259–267.
- (14) Pan, Y.; Liu, Y.; Zeng, G.; Zhao, L.; Lai, Z. Rapid Synthesis of Zeolitic Imidazolate Framework-8 (ZIF-8) Nanocrystals in an Aqueous System. *Chem. Commun.* **2011**, *47*, 2071–2073.
- (15) Kim, Y. J.; Kim, M.-Z.; Alam, S. F.; Rehman, A.; Devipriyanka, A.; Sharma, P.; Lee, H. R.; Cho, C.-H. Polarity-Dependent Particle Size of Zeolitic Imidazolate Framework Synthesized in Various Solvents. *Mater. Chem. Phys.* **2021**, *259*, 124021.
- (16) Galletti, G.; Prete, P.; Vanzini, S.; Cucciniello, R.; Fasolini, A.; De Maron, J.; Cavani, F.; Tabanelli, T. Glycerol Carbonate as a Versatile Alkylating Agent for the Synthesis of β -Aryloxy Alcohols. *ACS Sustain. Chem. Eng.* **2022**, *10*, 10922–10933.
- (17) Tabanelli, T.; Giliberti, C.; Mazzoni, R.; Cucciniello, R.; Cavani, F. An Innovative Synthesis Pathway to Benzodioxanes: The Peculiar Reactivity of Glycerol Carbonate and Catechol. *Green Chem.* **2019**, *21*, 329–338.
- (18) Anastas, P. T.; Warner, J. C. *Green Chemistry: Theory and Practice*; Oxford University Press, 1998.
- (19) Cucciniello, R.; Anastas, P. T. Design for Degradation or Recycling for Reuse? *Curr. Opin. Green Sustain. Chem.* **2021**, *31*, 100528.
- (20) Cespi, D.; Cucciniello, R.; Ricciardi, M.; Capacchione, C.; Vassura, I.; Passarini, F.; Proto, A. A Simplified Early Stage Assessment of Process Intensification: Glycidol as a Value-Added Product from Epichlorohydrin Industry Wastes. *Green Chem.* **2016**, *18*, 4559–4570.
- (21) Sonnati, M. O.; Amigoni, S.; de Givenchy, E. P. T.; Darmanin, T.; Choulet, O.; Guittard, F. Glycerol Carbonate as a Versatile Building Block for Tomorrow: Synthesis, Reactivity, Properties and Applications. *Green Chem.* **2013**, *15*, 283–306.
- (22) Pescarmona, P. P. Cyclic Carbonates Synthesised from CO₂: Applications, Challenges and Recent Research Trends. *Curr. Opin. Green Sustain. Chem.* **2021**, *29*, 100457.
- (23) Holló, G.; Zámbo, D.; Deák, A.; Rossi, F.; Cucciniello, R.; Lo Nostro, P.; Nabika, H.; Baytekin, B.; Lagzi, I.; Itatani, M. Effect of the Polarity of Solvents on Periodic Precipitation: Formation of Hierarchical Revert Liesegang Patterns. *J. Phys. Chem. B* **2022**, *126*, 8322–8330.
- (24) de Caro, P.; Bandres, M.; Urrutigoity, M.; Cecutti, C.; Thiebaud-Roux, S. Recent Progress in Synthesis of Glycerol Carbonate and Evaluation of Its Plasticizing Properties. *Front. Chem.* **2019**, *7*, 308.
- (25) Valletti, N.; Acar, M.; Cucciniello, R.; Magrini, C.; Budroni, M. A.; Tatini, D.; Proto, A.; Marchettini, N.; Lo Nostro, P.; Rossi, F. Glycerol Carbonate Structuring in Aqueous Solutions as Inferred from Mutual Diffusion Coefficient, Density and Viscosity Measurements in the Temperature Range 283.15–313.15 K. *J. Mol. Liq.* **2022**, *357*, 119114.
- (26) Shi, Z.; Yu, Y.; Fu, C.; Wang, L.; Li, X. Water-Based Synthesis of Zeolitic Imidazolate Framework-8 for CO₂ Capture. *RSC Adv.* **2017**, *7*, 29227–29232.
- (27) García-Palacín, M.; Martínez, J. I.; Pasetta, L.; Deacon, A.; Johnson, T.; Malankowska, M.; Téllez, C.; Coronas, J. Sized-Controlled ZIF-8 Nanoparticle Synthesis from Recycled Mother Liquors: Environmental Impact Assessment. *ACS Sustain. Chem. Eng.* **2020**, *8*, 2973–2980.

(28) Tezerjani, A. A.; Halladj, R.; Askari, S. Different View of Solvent Effect on the Synthesis Methods of Zeolitic Imidazolate Framework-8 to Tuning the Crystal Structure and Properties. *RSC Adv.* **2021**, *11*, 19914–19923.

(29) Fantoni, T.; Tolomelli, A.; Cabri, W. A Translation of the Twelve Principles of Green Chemistry to Guide the Development of Cross-Coupling Reactions. *Catal. Today* **2022**, *397–399*, 265–271.

(30) Zhang, Y.; Jia, Y.; Li, M.; Hou, L. Influence of the 2-Methylimidazole/Zinc Nitrate Hexahydrate Molar Ratio on the Synthesis of Zeolitic Imidazolate Framework-8 Crystals at Room Temperature. *Sci. Rep.* **2018**, *8*, 9597.

(31) Pan, Y.; Heryadi, D.; Zhou, F.; Zhao, L.; Lestari, G.; Su, H.; Lai, Z. Tuning the Crystal Morphology and Size of Zeolitic Imidazolate Framework-8 in Aqueous Solution by Surfactants. *CrystEngComm* **2011**, *13*, 6937–6940.

(32) Zheng, G.; Chen, Z.; Sentosun, K.; Pérez-Juste, I.; Bals, S.; Liz-Marzán, L. M.; Pastoriza-Santos, I.; Pérez-Juste, J.; Hong, M. Shape Control in ZIF-8 Nanocrystals and Metal Nanoparticles@ZIF-8 Heterostructures. *Nanoscale* **2017**, *9*, 16645–16651.

(33) Cravillon, J.; Münzer, S.; Lohmeier, S.-J.; Feldhoff, A.; Huber, K.; Wiebcke, M. Rapid Room-Temperature Synthesis and Characterization of Nanocrystals of a Prototypical Zeolitic Imidazolate Framework. *Chem. Mater.* **2009**, *21*, 1410–1412.

(34) Chen, Y.; Tang, S. Solvothermal Synthesis of Porous Hydrangea-like Zeolitic Imidazole Framework-8 (ZIF-8) Crystals. *J. Solid State Chem.* **2019**, *276*, 68–74.

(35) Dúzs, B.; Holló, G.; Schusztzer, G.; Horváth, D.; Tóth, Á.; Szalai, I.; Lagzi, I. Synthesis of Zeolitic Imidazolate Framework-8 and Gold Nanoparticles in a Sustained Out-of-Equilibrium State. *Sci. Rep.* **2022**, *12*, 222.

(36) Lee, Y.-R.; Jang, M.-S.; Cho, H.-Y.; Kwon, H.-J.; Kim, S.; Ahn, W.-S. ZIF-8: A Comparison of Synthesis Methods. *Chem. Eng. J.* **2015**, *271*, 276–280.

(37) He, M.; Yao, J.; Liu, Q.; Wang, K.; Chen, F.; Wang, H. Facile Synthesis of Zeolitic Imidazolate Framework-8 from a Concentrated Aqueous Solution. *Microporous Mesoporous Mater.* **2014**, *184*, 55–60.

(38) Parulkar, A.; Brunelli, N. A. High-Yield Synthesis of ZIF-8 Nanoparticles Using Stoichiometric Reactants in a Jet-Mixing Reactor. *Ind. Eng. Chem. Res.* **2017**, *56*, 10384–10392.

(39) Sarri, F.; Tatini, D.; Tanini, D.; Simonelli, M.; Ambrosi, M.; Ninham, B. W.; Capperucci, A.; Dei, L.; Lo Nostro, P. Specific Ion Effects in Non-Aqueous Solvents: The Case of Glycerol Carbonate. *J. Mol. Liq.* **2018**, *266*, 711–717.

(40) Ostad, M. I.; Shahrak, M. N.; Galli, F. The Influence of Different Synthetic Solvents on Photocatalytic Activity of ZIF-8 for Methanol Production from CO₂. *Microporous Mesoporous Mater.* **2021**, *326*, 111363.

(41) Cucciniello, R.; Cespi, D. Recycling within the Chemical Industry: The Circular Economy Era. *Recycling* **2018**, *3*, 22.

(42) Cho, H.-Y.; Kim, J.; Kim, S.-N.; Ahn, W.-S. High Yield 1-L Scale Synthesis of ZIF-8 via a Sonochemical Route. *Microporous Mesoporous Mater.* **2013**, *169*, 180–184.

(43) Jiménez-González, C.; Poehlauer, P.; Broxterman, Q. B.; Yang, B.-S.; am Ende, D.; Baird, J.; Bertsch, C.; Hannah, R. E.; Dell'Orco, P.; Noorman, H.; Yee, S.; Reintjens, R.; Wells, A.; Massonneau, V.; Manley, J. Key Green Engineering Research Areas for Sustainable Manufacturing: A Perspective from Pharmaceutical and Fine Chemicals Manufacturers. *Org. Process Res. Dev.* **2011**, *15*, 900–911.

(44) Cespi, D.; Beach, E. S.; Swarr, T. E.; Passarini, F.; Vassura, I.; Dunn, P. J.; Anastas, P. T. Life Cycle Inventory Improvement in the Pharmaceutical Sector: Assessment of the Sustainability Combining PMI and LCA Tools. *Green Chem.* **2015**, *17*, 3390–3400.

(45) Sheldon, R. A. The E Factor at 30: A Passion for Pollution Prevention. *Green Chem.* **2023**, *25*, 1704–1728.

(46) Butova, V. V.; Budnyk, A. P.; Bulanova, E. A.; Lamberti, C.; Soldatov, A. V. Hydrothermal Synthesis of High Surface Area ZIF-8 with Minimal Use of TEA. *Solid State Sci.* **2017**, *69*, 13–21.

(47) Awadallah-F, A.; Hillman, F.; Al-Muhtaseb, S. A.; Jeong, H.-K. On the Nanogate-Opening Pressures of Copper-Doped Zeolitic

Imidazolate Framework ZIF-8 for the Adsorption of Propane, Propylene, Isobutane, and n-Butane. *J. Mater. Sci.* **2019**, *54*, 5513–5527.

(48) Joaristi, A. M.; Juan-Alcañiz, J.; Serra-Crespo, P.; Kapteijn, F.; Gascon, J. Electrochemical Synthesis of Some Archetypical Zn²⁺, Cu²⁺, and Al³⁺ Metal Organic Frameworks. *Cryst. Growth Des.* **2012**, *12*, 3489–3498.

(49) Shi, Q.; Chen, Z.; Song, Z.; Li, J.; Dong, J. Synthesis of ZIF-8 and ZIF-67 by Steam-Assisted Conversion and an Investigation of Their Tribological Behaviors. *Angew. Chem., Int. Ed.* **2011**, *50*, 672–675.

Recommended by ACS

Preparation, Characterization, and Application of Metal Oxide-Doped Zeolitic Imidazolate Framework

Fulya Kümbetlioglu, Ayten Ateş, *et al.*

JULY 20, 2023
ACS OMEGA

READ 

Aqueous Stability of Metal–Organic Frameworks Using ReaxFF-Based Metadynamics Simulations

Yongjian Yang, John C. Mauro, *et al.*

JULY 07, 2023
THE JOURNAL OF PHYSICAL CHEMISTRY B

READ 

Green Synthesis Approaches toward Preparation of ZIF-76 and Its Thermal Behavior

Marija Švegovc, Nataša Zabukovec Logar, *et al.*

APRIL 20, 2023
CRYSTAL GROWTH & DESIGN

READ 

Polyaniline-Coated ZIF-67-Derived Co/C Nanostructures for Efficient Electromagnetic Wave Absorption

Guiyang Xian, Lingbing Kong, *et al.*

MAY 14, 2023
ACS APPLIED NANO MATERIALS

READ 

Get More Suggestions >